

3D FINITE ELEMENT SIMULATION OF RESIDUAL STRESSES IN UIC60 RAILS DURING THE QUENCHING PROCESS

by

*Reza MASOUDI NEJAD, Mahmoud SHARIATI**, and *Khalil FARHANGDOOST*

Faculty of Engineering, Department of Mechanical Engineering, Ferdowsi University of Mashhad,
Mashhad, Iran

Original scientific paper
DOI:

The aim of this paper is to develop means to predict accurately the residual stresses due to quenching process of an UIC60 rail. A three-dimensional nonlinear stress analysis model has been applied to estimate stress fields of an UIC60 rail in the quenching process. A cooling mechanism with water spray is simulated applying the elastic–plastic finite element analysis for the rail. The three-dimensional finite element analysis results of the studies presented in this paper are needed to describe the initial conditions for analyses of how the service conditions may act to change the as-manufactured stress field.

Keywords: residual stress, stress field, quenching process, thermal load.

Introduction

The residual stresses of railroad rails are influenced by the heat treatment during the manufacturing process. In recent decades, numerous studies have attempted to estimate the residual stresses. Masoudi Nejad [1] estimated the residual stresses resulted from heat treatment in the railway mono-block wheels by an elastic–plastic three dimensional finite element model. The obtained results from this study have shown that the residual stresses' values obtained from the heat treatment are of significant values and their effect on the crack initiation and fatigue life cannot be disregarded [2]. Masoudi Nejad et al. [3] presented a three-dimensional elastic-plastic finite element simulation for the estimation of residual stresses resulting from the manufacturing process and service condition in wheels of railroad in Iran railroad. Masoudi Nejad [4] investigated the stress distribution due to press

* Corresponding author; e-mail: mshariati44@um.ac.ir, reza.masoudinejad@gmail.com.

fitting process of a bandage wheel and mechanical residual stresses due to wheel/rail operation. Finally, the effect of residual stresses on the fatigue life is assessed using the damage mechanics methods. Salehi et al [5] presented the prediction of fatigue life and crack propagation in a bandage wheel due to the stress field caused by mechanical loads and press fitting process of a bandage wheel.

The object of several investigations on manufacturing processes is to show a layer of compressive residual stress on the surface of parts to inhibit propagation of cracks. The effects of the residual stress and metal removal on the contact fatigue life have been estimated by Seo et al. [6, 7]. Okagata [8] evaluated the fatigue strength of Japanese railway wheel and presented the fatigue design method of the high-speed railway wheel by considering the effect of manufacturing conditions on the fatigue strength of the material. In the literature [9–15], some of these issues are studied using some experimental observations, analytical calculations and FEA calculations within various contexts.

Biempica et al. [16] provides a detailed study of the development of residual stresses in an UIC-60 rail and their reduction by means of roller straightening. Ringsberg and Lindback [17] carried out a three-dimensional analysis to determine the residual stresses that appear during cooling and straightening. Zhan et al. [18] described an improved rail-head hardening technology with adopting new induction heating coil, new coolant and cooling devices and new cooling mechanism. The work of Skyttebol et al. [19] represents a complete description of the Finite Element technique application for prediction of residual stresses in a flash-butt welded rail.

Most of the previous studies described above have estimated the residual stresses using numerical simulations and finite element method in the rail. Unfortunately, existing techniques for estimation of residual stresses of the rail problems are simple models. Finite element models of this nature generally need a fine mesh to obtain accurate results [20-22]. The simple model cannot obtain accurate stress field results of rail under the influence of thermal loads. In this paper, a three-dimensional elastic-plastic finite element method, using the true geometry of an UIC60 rail, has been used to model and accurately predict the stress distribution due to the quenching process. The quenching process simulation consisted of two parts, a nonlinear transient thermal analysis and a nonlinear static structural analysis. The heat treatment process cools the head of the rail much faster

than its web. The head of the rail is sprayed with water. The web of the rail has not been cooled as rapidly.

Finite element modeling and residual stress

Residual stresses can be induced during the manufacturing of a rail, typically to improve its performance. Those stresses can be modified by service loading, sometimes to such an extent that the benefits of the manufacturing stresses are completely negated. However, this process generates the higher tensile hoop stress that could contribute to appearance of the rail-head fatigue cracks. They reduce the fatigue strength and exacerbate the effect of cracks and material defects. The rail made of the UIC60 profiles that are currently utilized in railway system was selected. The rail UIC60 profile is shown in Fig. 1. The rail length equals the length between the two sleepers and is equal to 600 mm. Due to symmetry of the rail, only one half of the distance is modeled. For the stress analysis in railway rail, the three-dimensional elastic-plastic finite element method is used. In Fig. 2 is shown the elastic-plastic behavior at different temperatures using a bilinear isotropic hardening model. In this simulation for residual stress, the two parts of analysis used: the non-linear thermal analysis and the non-linear static structural analysis. The non-linear thermal analysis determined the temperature distribution of the rail that varies over time, was used as an input load for the non-linear static structural analysis. In finite element software, exists the possibility to use the thermal analysis of a model for structural solution. Fig. 3 shows the finite element modeling of a rail in manufacturing process, for residual stress analysis. The model mesh has 16421 eight-nodded elements with three translational degrees of freedom at each node with quarter point node locations.

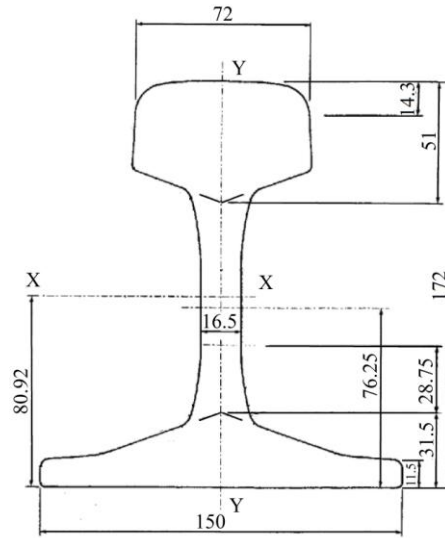


Figure 1. Rail profile, type UIC60 (in mm)

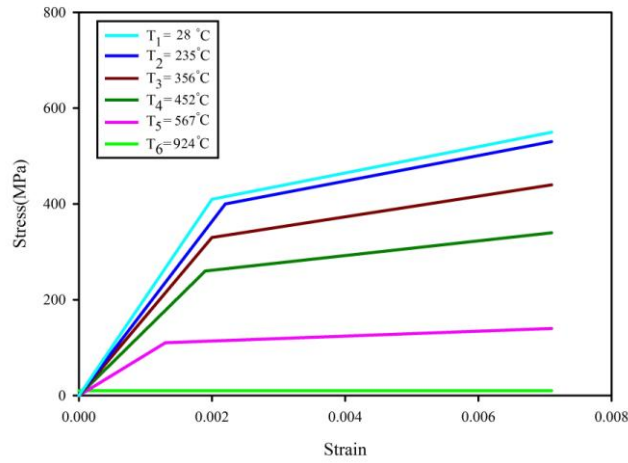


Figure 2. Mechanical material data for railway rail

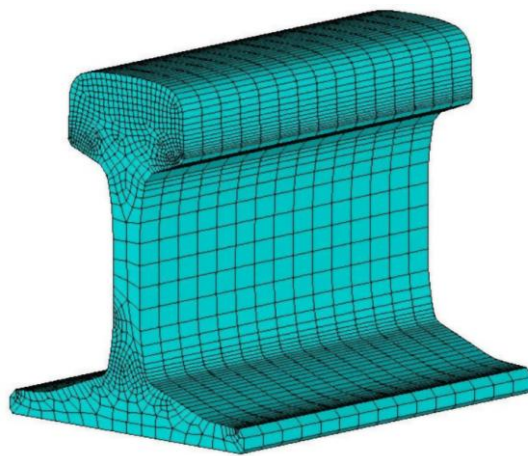


Figure 3. Finite element modeling of rail

The quenching process consists of several steps, each of which imposes different boundary conditions on the model. A schematic of the process is shown in Fig. 4, which represents the ambient environment imposed on the rail head. The rail is assumed to be initially at a uniform temperature (921°C). The quenching process consists of six nozzles; the upper surface of the rail has three nozzles, and each side of rail has a nozzle and the bottom has a nozzle. Conduction in the rail itself occurs during the quenching process. The input parameters included material properties, temperatures, time and boundary conditions, which were thought to affect the residual stress field. The parameters required for the analysis of the heat transfer, included the thermal conductivity and specific heat. Thermal conductivity k , the ability of the material to conduct heat energy, is described. This value variation with temperature is given as an input to the application. Since this was the heat transfer analysis, including the free expansion, so the specific heat at constant pressure of the material (c_p) is used. In this paper, the density is constant and equal to 7860 kg/m^3 were considered. The heat capacity variation with temperature has been defined as input for the software. The convection occurs from all the rail surfaces during the quenching process. The heat transfer coefficient for rail to air is $27 \text{ W/m}^2\text{C}$ and the heat transfer coefficient for the portion of the rail tread, which is exposed to the water spray during the quenching process, is $3042 \text{ W/m}^2\text{C}$. Radiation from all surfaces of the rail is permitted during the heat transfer analysis. For this purpose, two parameters are used to determine the radiation heat transfer: the Stefan-Boltzmann constant, $\sigma = 5.67 \times 10^{-8} \text{ W/m}^2\text{K}^4$ and the surface emissivity, $\varepsilon = 0.96$.

One of the most important factors in residual stress forming is a type of constraint in the structure, which means that the two different displacement boundary condition show different residual stresses. In this analysis, two sides of the rail are bounded by using the displacement boundary condition.

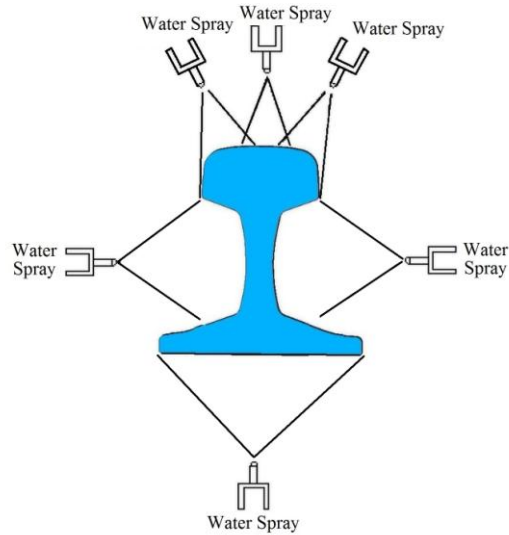


Figure 4. The schematic diagram of the cooling mechanism

Results and discussion

Fig. 5. shows the temperature-time histories of three nodes in the model (on the head surface of the rail, the web of the rail and another at the foot of the rail), beginning at the initial temperature (921 °C), through the quenching, and finally to room temperature at the end of the cooling down.

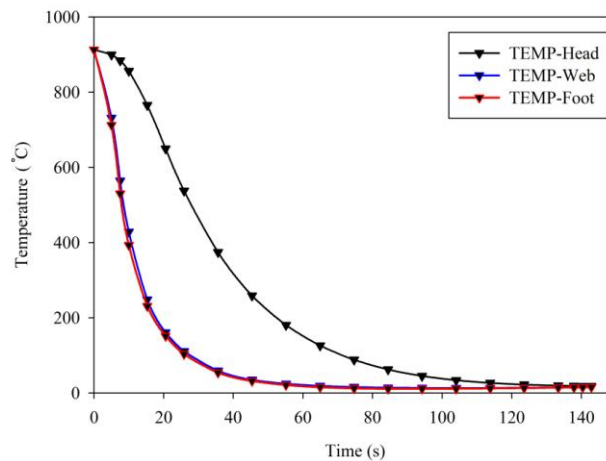


Figure 5. Baseline temperature-time history of three nodes during the quenching process

The non-linear transient thermal analysis yields the time-dependent temperature field, which causes the estimation of the residual stresses, since the temperature varies with location and time. As already mentioned in the analysis of air and water heat transfer coefficients are assumed constant. Fig. 6 shows the temperature distribution due to the quenching process in the thermal model. According to Fig. 6, the effects of water spray on the rail cooling are visible.

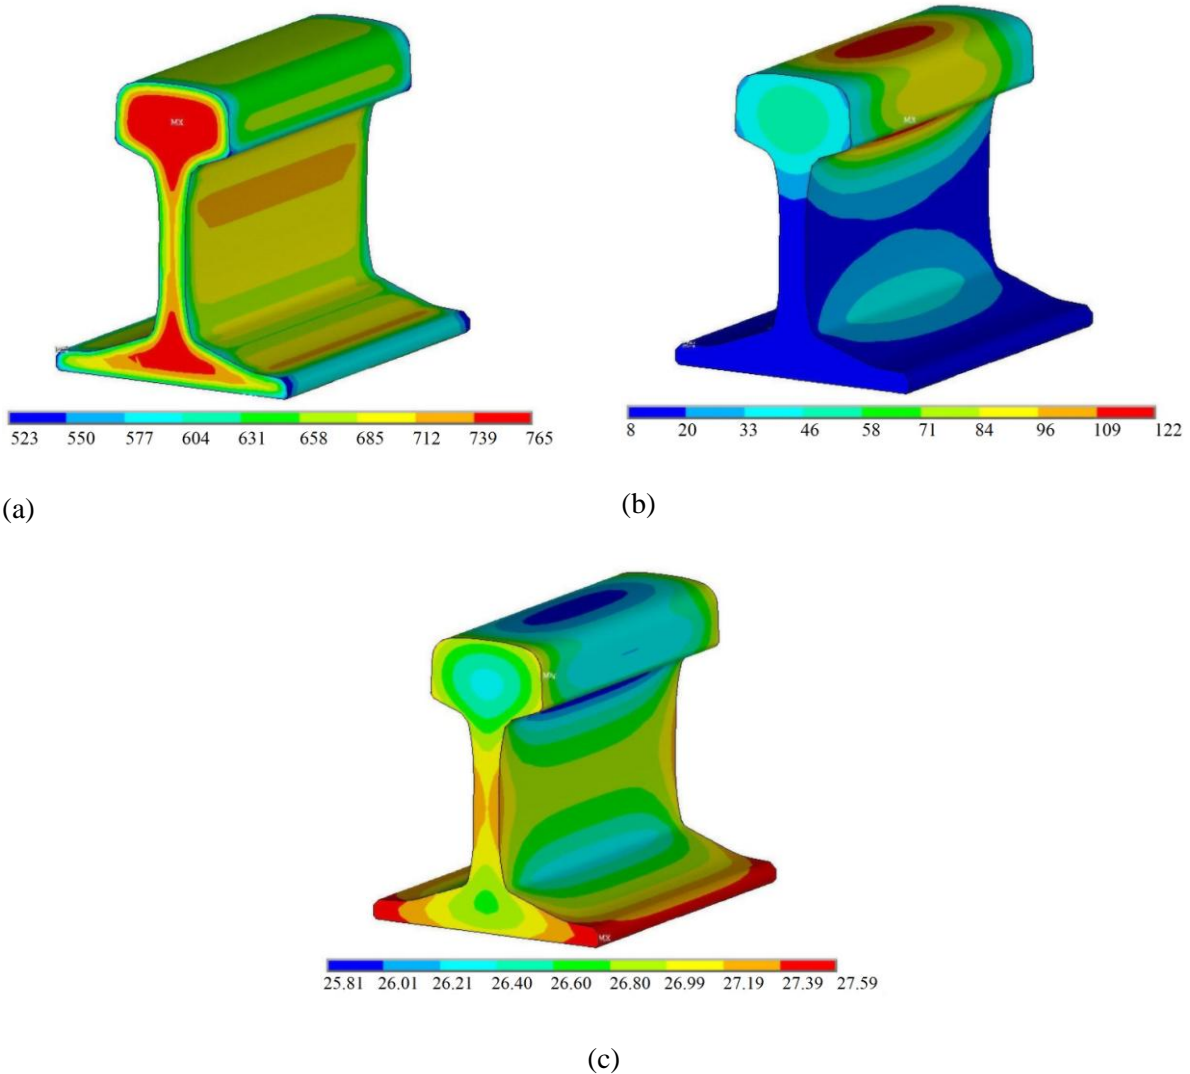


Figure 6. Contour plots of the temperature distribution (in °C) due to the quenching process: (a) $t = 5(s)$, (b) $t = 75(s)$, (c) $t = 150(s)$.

Fig. 7 illustrates the contour plots of the stress field. For UIC60 rails, the magnitude of von Mises stress appears to be 639 MPa, after this process, and the tendency of von Mises stress is not symmetrical at the upper and the bottom side. The magnitude of this stress is higher than the yield strength of the steel rail, since the rail is plastically deforming. The residual tension at the rail-head surface, which tends to initiate cracks opening, will promote their growth through the tensile layer. Thus, this analysis shows that the fatigue cracks were initiated at a depth of 14 mm below rail-head surface.

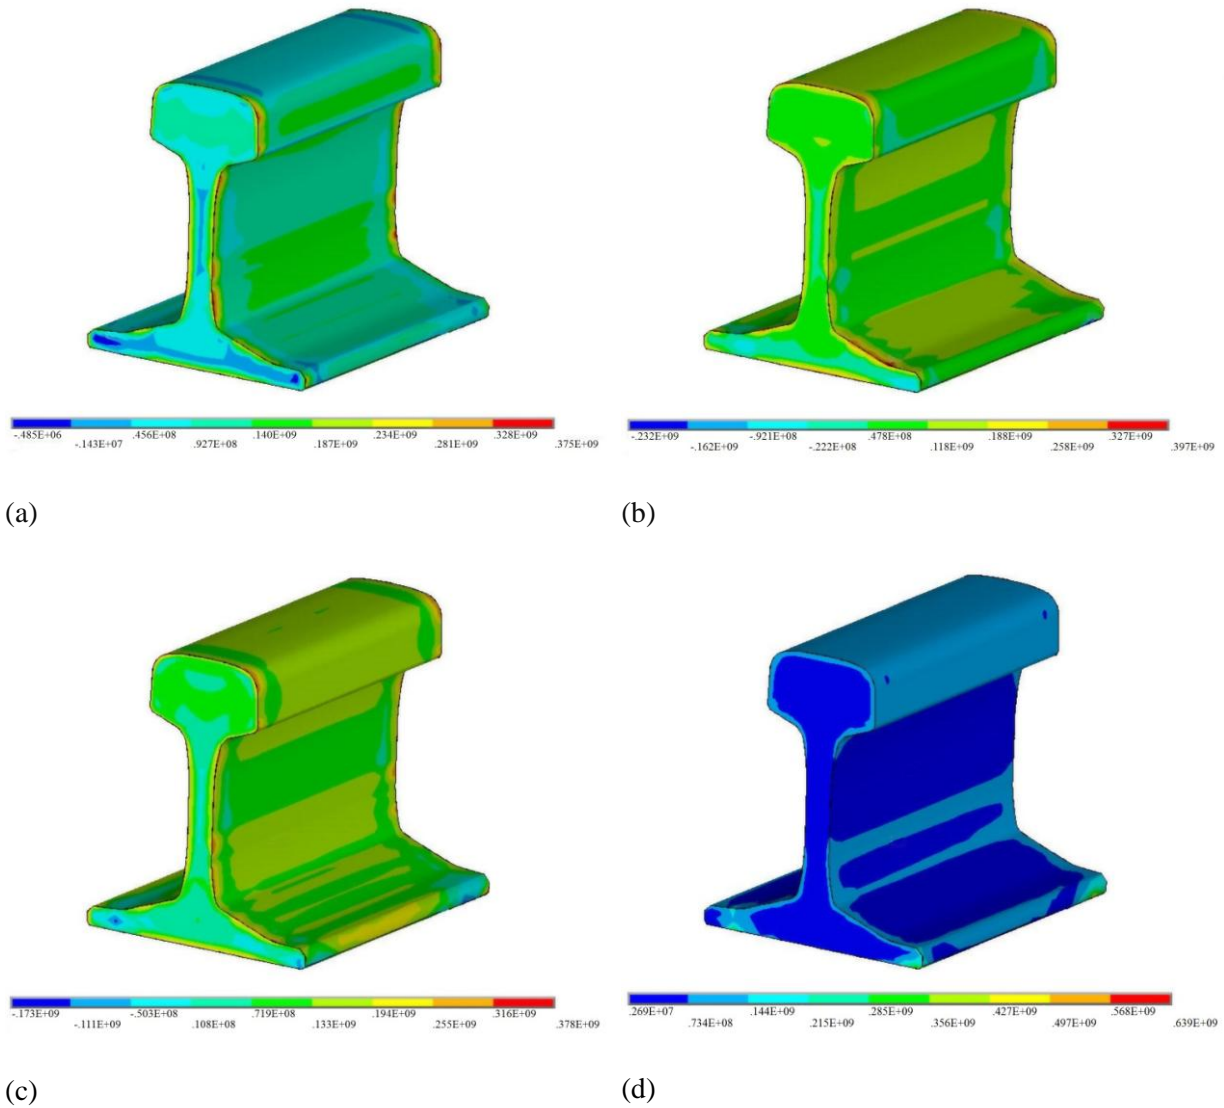


Figure 7. Stress field due to the quenching process of rail analysis; (a) x-direction (b) y-direction (c) z-direction (d) von Mises.

The variation of the stress distribution over the rail-head width, during the quenching process, as a result of the thermal gradient, is plotted in Fig. 8. The vertical axis in Fig. 8 denotes stress (MPa) and the horizontal axis is rail-head width (mm). The residual stresses of the rail height from FEM approach are presented in Fig. 9. The maximum axial stress, for a given probability, can be obtained from Fig. 9. The maximum axial stress for the baseline model is 241 MPa.

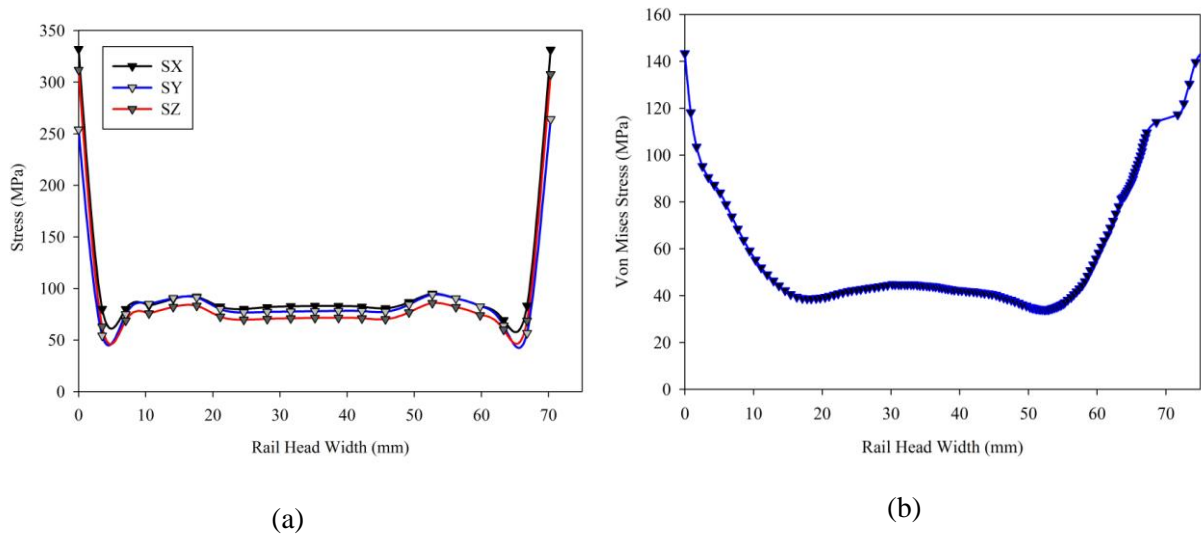


Figure 8. Stress distribution over the rail-head width during the quenching process: (a) the x, y and z-direction (b) von Mises

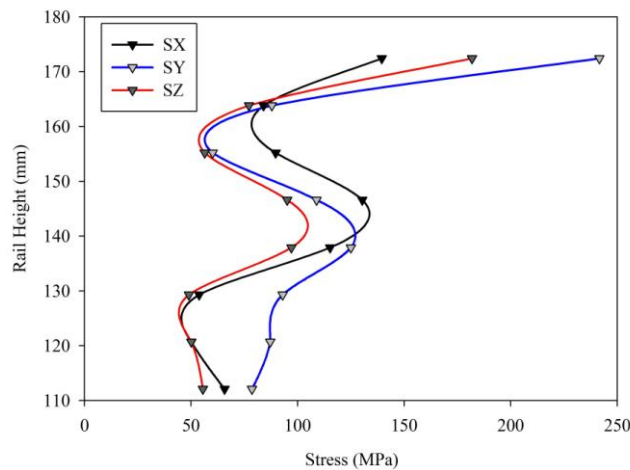


Figure 9. Stress in terms of the rail height

Conclusions

The three-dimensional finite element analysis for simulation of residual stresses in UIC60 rails is developed in this paper, which is based on the residual stresses from the quenching process. For this purpose, the non-linear 3-D finite element analysis is used for residual stress. The following conclusions can be drawn:

- 1- The finite element analysis results show the very significant stress distribution. The resultant stress field has a high value and its effects are not negligible for the crack initiation.

- 2- The results revealed that the stress field is highly sensitive to the variable thermal loads. Therefore, this factor significantly affects the stress field of rails during the quenching process.
- 3- The results confirmed the magnitude of the stress in the rail since this has been identified as a reasonable means of assessing the possibility of fatigue cracks to initiate.
- 4- The UIC60 rails are rail-quenched using a water spray to induce the beneficial residual compressive stress at the rail-head surface.
- 5- Results of the baseline analysis suggest the presence of a 14 mm thick residual stress layer with stresses as high as 639 MPa in an UIC60 rail. Therefore, the residual stresses have a significant effect on the fatigue life.

In this paper, the residual stresses in the rail caused by the stress field from the quenching process of an UIC60 rail have been investigated. In the further future work, a quantitative comparison between detailed FEA and experimentally measured strain and rail deformation will be presented. In addition, other effects, such as the process parameters, boundary conditions and material properties need to be included in the rail.

References

- [1] Masoudi Nejad, R., Using three-dimensional finite element analysis for simulation of residual stresses in railway wheels, *Engineering Failure Analysis*, 45(2014), pp. 449-455. <http://dx.doi.org/10.1016/j.engfailanal.2014.07.018>
- [2] Masoudi Nejad, R., Farhangdoost, Kh, Shariati, M., Numerical study on fatigue crack growth in railway wheels under the influence of residual stresses, *Engineering Failure Analysis*, 52(2015), pp. 75-89. <http://dx.doi.org/10.1016/j.engfailanal.2015.03.002>
- [3] Masoudi Nejad, R, Salehi, S.M, Farrahi, G.H., Simulation of railroad crack growth life under the influence of combination mechanical contact and thermal loads, in *3rd International Conference on Recent Advances in Railway Engineering*, Tehran, Iran, 2013. <http://dx.doi.org/10.13140/2.1.1688.2723>

- [4] Masoudi Nejad R. Rolling contact fatigue analysis under influence of residual stresses. MS Thesis, School of Mechanical Engineering, *Sharif University of Technology*, Tehran, Iran, 2013. <http://dx.doi.org/10.13140/RG.2.1.1884.8800/1>
- [5] Salehi, S.M, Farrahi, G.H, Sohrabpoor, S, Masoudi Nejad, R., Prediction of fatigue life in the railway wheels under the influence of residual stress field, *International Journal of Railway Research*, 1(2014), 1, pp. 61-72.
- [6] Seo, JW, Goo, BC, Choi, JB, Kim, YJ., Effect of removal and residual stress on the contact fatigue life of railway wheels, *International Journal of Fatigue*, 30(2008), 10-11, pp. 115–21.
- [7] Seo, JW, Kwon, S J, Jun, HK, Lee, DH., Effects of residual stress and shape of web plate on the fatigue life of railway wheels, *Engineering Failure Analysis*, 16(2009), pp. 2493–2507.
- [8] Okagata, Y, Kiriyama, K, Kato, T., Fatigue strength evaluation of the Japanese railway wheel, *Fatigue Fract Eng Mater Struct*, 30(2007), pp. 356–71.
- [9] Siva, N., Lingamanaik, Bernard, Chen, K., Prediction of residual stresses in low carbon bainitic–martensitic railway wheels using heat transfer coefficients derived from quenching experiments, *Computational Materials Science*, 77(2013), pp. 153–160.
- [10] Siva, N., Lingamanaik, Bernard, Chen, K., Thermo-mechanical modeling of residual stresses induced by martensitic phase transformation and cooling during quenching of railway wheels, *Journal of Materials Processing Technology*, 211(2011), 9, pp. 1547–52.
- [11] Kaiser, R., et al., Experimental characterization and modeling of triaxial residual stresses in straightened railway rails, *The Journal of Strain Analysis for Engineering Design*, 50(2015), 3, pp. 190-198.
- [12] Jun, TS, Hofmann, F, Belnoue, J, et al., Triaxial residual strains in a railway rail measured by neutron diffraction, *The Journal of Strain Analysis for Engineering Design*, 44(2009), 7, pp. 563–568.
- [13] Mansouri, H., Monshi, A., Hadavinia, H., Effect of local induction heat treatment on the induced residual stresses in the web region of a welded rail, *The Journal of Strain Analysis for Engineering Design*, 39(2004), 3, pp. 271-283.

- [14] Seo, J. W., Kwon, S. J., Jun, H. K., Lee, D. H., Effects of residual stress and shape of web plate on the fatigue life of railway wheels, *Engineering Failure Analysis*, 16(2009), 7, pp. 2493–507.
- [15] Tawfik, D., Mutton, P. J., Chiu, W.K., Experimental and numerical investigations: Alleviating tensile residual stresses in flash-butt welds by localized rapid post-weld heat treatment, *Journal of Materials Processing Technology*, 196(2008), 1-3, pp. 279–91.
- [16] Biempica, C. B., del Coz Díaz, J. J., Nieto, P. G., Sánchez, I. P., Nonlinear analysis of residual stresses in a rail manufacturing process by FEM, *Applied Mathematical Modeling*, 33(2009), 1, pp. 34-53.
- [17] Ringsberg, J.W., Lindbäck, T., Rolling contact fatigue analysis of rails including numerical simulations of the rail manufacturing process and repeated wheel-rail contact loads, *International Journal of fatigue*, 25(2003), 6, pp. 547-558.
- [18] Zhan X., Wang S., Research on the improvement of rail head hardening technology on railway, *Proceedings of the Eastern Asia Society for Transportation Studies*, 2005.
- [19] Skyttebol A, Josefson B.L, Ringsberg J.W., Fatigue crack growth in a welded rail under the influence of residual stresses, *Engineering Fracture Mechanics*, 72(2005), 2, pp. 271-285.
- [20] Masoudi Nejad, R, Salehi, SM, Farrahi, GH, Chamani, M., Simulation of crack propagation of fatigue in Iran rail road wheels and Effect of residual stresses, in *Proceedings of the 21st International Conference on Mechanical Engineering*, Tehran, Iran, 2013. (In Persian). <http://dx.doi.org/10.13140/2.1.3785.4244>
- [21] Masoudi Nejad, R., Shariati, M., Farhangdoost, Kh., Effect of wear on rolling contact fatigue crack growth in rails, *Tribology International*, 94(2016), pp. 118-125. <http://dx.doi.org/10.1016/j.triboint.2015.08.035>
- [22] Hadipour, M., Alambeigi, F., Hosseini, R., Masoudinejad, R., A study on the vibrational effects of adding an auxiliary chassis to a 6-ton truck, *Journal of American Science*, 7(2011), 6, pp. 1219–1226.