

EFFECT OF CONCENTRATION OF METAL INORGANIC SALT ON FIBER DIAMETER IN ELECTROSPINNING PROCESS Mathematical Model and Experimental Verification

by

Chun-Hui HE^{a,b*}, Peng LIU^a, and Hong-Yan LIU^c

^a National Engineering Laboratory for Modern Silk, College of Textile and Clothing Engineering,
Soochow University, Suzhou, China

^b Department of Chemistry, Xi'an JiaoTong-Liverpool University, Suzhou, China

^c School of Fashion Technology, Zhongyuan University of Technology, Zhengzhou, China

Original scientific paper

<https://doi.org/10.2298/TSCI160324291H>

Electrospinning is used to produce polyvinylidene fluoride nanofibers under various ferric chloride contents. Effect of the ferric chloride concentration on fiber diameter is investigated theoretically and experimentally. A critical value of the concentration is found, below which fiber diameter decreases with its concentration, and an opposite prediction is observed when the concentration is larger than the critical value.

Key word: *electrospinning, fiber diameter, metal inorganic salt*

Introduction

Electrospinning is a micro/nano scale flow, which is widely used to fabricate fibrous materials with diameters ranging from several micrometers to a few nanometers from a polymer solution [1-4]. In this process, a jet is ejected and accelerated from a spinneret by a high electrostatic force, and then deposited on a grounded-metal collector as a nanofiber, which can be widely used in many high-tech areas where the fiber diameter is crucial to its applications. The fiber diameter mainly depends on solution properties, *e. g.* the viscosity, conductivity, surface tension, and others [5-8]. In the electrospinning process, additive (*e. g.* metal inorganic salt) is a versatile method to change the solution property and to control fiber morphology. Alpha-Fe₂O₃ [9], Na₂CO₃ [10], Cu nanoparticles [11], milk [12], and chitosan [13] were used in practical applications. In this study FeCl₃ will be used as an additive, due to its inexpensive price and ferromagnetic property.

The electrospinning has been developing very fast, and various new technologies were appeared recently, for examples, the bubble electrospinning [14, 15] and bubbfil spinning [3], which are the promising technologies for mass-production of nanofibers, and new applications of nanofibers have been appeared, for examples, oxygen-enrichment nanofiber membrane [16] and nanofiber membrane for enhancing silver ion release [17].

This paper will prepare for polyvinylidene fluoride (PVDF) fibrous membrane with different FeCl₃ contents via electrospinning. At the same time, the influence of FeCl₃ concentration on fiber diameter of electrospun PVDF fibrous material will be studied. Finally, a

* Corresponding author, e-mail: mathew_he@yahoo.com

mathematical model of the relationship between the FeCl_3 concentration and fiber diameter is proposed and experimentally verified.

Experiment

In this work, PVDF particles were dissolved in N,N-dimethylacetamide (DMF), and acetone (ACE) mixtures (weight ratio 1:1) under constant and vigorous magnetic stirring. Subsequently, FeCl_3 with different contents were added, respectively, into mentioned solution and kept vigorous magnetic stirring at room temperature. The concentration of FeCl_3 (*i. e.*, 2 wt.%, 4 wt.%, 6 wt.%, 8 wt.%, and 10 wt.%) in the mixture was based on the weight of PVDF, DMF, and ACE. In this experiment, all solutions were the concentration of PVDF 6 wt.% and chemicals were used without further purification. In the spinning process, the applied electric voltage is 25 kV and the collector distance is 15 cm. All the experiments were performed at similar ambient temperature and relatively humidity.

Theoretical analysis and experimental verification

The SEM images of electrospun fibrous membrane with different FeCl_3 contents are presented in figs. 1(a)-1(f). It is obvious that electrospun pure PVDF nanofiber membrane shows beads on string morphology from fig. 1(a). Differently, there are no significant beads in the fibrous membrane from the solutions with a small amount of FeCl_3 , figs. 1(b), 1(c), and 1(d). Interestingly, when the FeCl_3 concentration was relatively high, lots of beads were appeared again. In addition, the surface becomes rough with the increase of FeCl_3 . Figures 1(e) and 1(f) clearly display this phenomenon. It was concluded that increased FeCl_3 concentration leads to poor spin-ability.

The diameter distribution curves of as-spun fibrous membrane with different FeCl_3 concentration have been demonstrated in fig. 1(g) and 1(l). It shows a narrow fiber diameter distribution at low FeCl_3 concentration, while wide fiber diameter distribution at relatively high-level. Meanwhile, it is obvious that the fibers diameter noticeably decreased in the relatively low-level FeCl_3 concentration and dramatically increased in the relatively high-level FeCl_3 concentration.

The fiber diameter is mainly influenced by conductivity, viscosity, and surface tension of the electrospinning solution. The properties of electrospinning solutions are displayed in tab. 1. It is clear that solution conductivity acutely increased while viscosity increased fiercely then decreased slightly at the beginning with the increasing of FeCl_3 concentration. However,

Table 1. Characteristics of the electrospinning solutions and the fiber diameters of the resultant fibrous membrane with different FeCl_3 concentration

FeCl_3 [wt.%]	Conductivity [$\mu\text{s cm}^{-1}$]	Viscosity ^a [Pas]	Surface tension ^b [Dyn cm^{-1}]	Diameter ^c [nm]
0	0.388	0.11	29.197 ± 0.029	64.8 ± 13.7
2	200.6	0.07	30.528 ± 0.029	55.2 ± 12.5
4	352.3	0.06	30.564 ± 0.014	66.9 ± 16.4
6	564.5	0.09	30.528 ± 0.013	95.8 ± 16.3
8	624.1	2.44	30.622 ± 0.013	172.5 ± 24.1
10	759.7	4.59	30.571 ± 0.029	219.7 ± 37.6

^a shear rate is 0.34 s^{-1} ; ^{b, c} values are expressed as means \pm SD

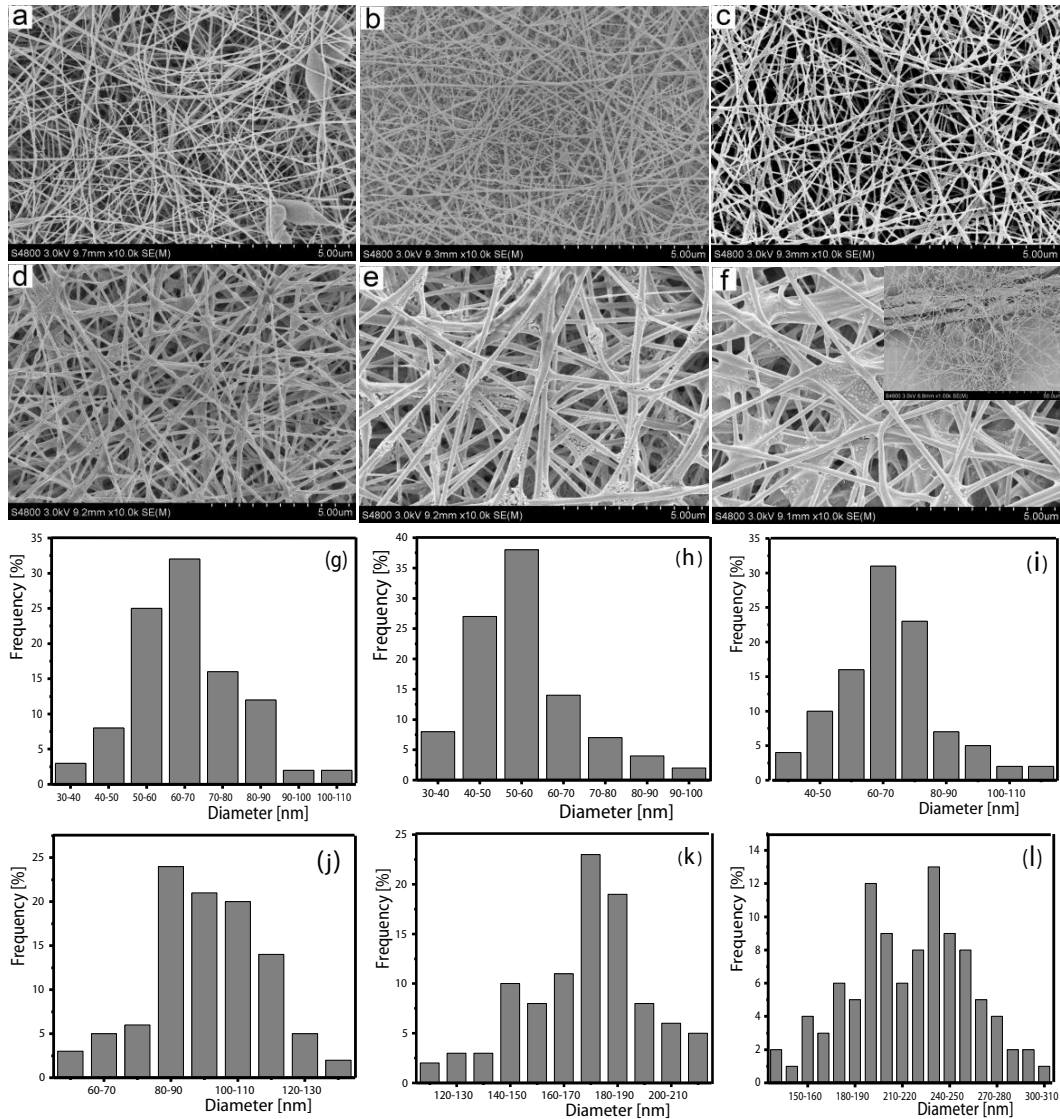


Figure 1. FESEM images and diameter distribution of the PVDF fibrous with different FeCl₃ contents: (a, g) 0, (b, h) 2, (c, i) 4, (d, j) 6, (e, k) 8, and (f, l) 10 wt.%

the surface tension of solution has no significant variation with the increase of FeCl₃ concentration.

Previous report [18, 19] indicated the diameter of electrospun fiber mainly depends upon solution viscosity, and higher viscosity leads to thicker fibers:

$$d \propto \eta^\alpha \quad (1)$$

where d is the fiber diameter, η – the viscosity, and α – a constant varying for different solutions.

On the other hand, higher concentration results in higher viscosity, which means [8]:

$$d \propto c^\beta, \quad c \leq c_0 \quad (2)$$

where c_0 is threshold value for c , β is a constant varying for different solutions.

We write:

$$d = k_1 + k_2c + k_3c^2 + k_4c^3 + \alpha(c), \quad c \leq c_0 \quad (3)$$

where k_i are constants to be further determined experimentally, $\alpha(c)$ is a matching term for $c > c_0$.

However, when the concentration increases to a threshold value, the electrospinning's spin-ability reduces, and when the concentration is larger than the threshold value, the fiber diameter increases greatly, which means:

$$d \propto \frac{1}{c^\delta}, \quad c \geq c_0 \quad (4)$$

where δ is a constant varying for different solutions.

We write:

$$d = \frac{1}{b_1 + b_2c + b_3c^2 + b_4c^3} + \beta(c), \quad c \geq c_0 \quad (5)$$

where the constants b_i are further determined experimentally, and $\beta(c)$ is a matching term for $c < c_0$.

Combining eq. (3) with eq. (5), we have the following relation between the fiber diameter and the concentration:

$$d = k_1 + k_2c + k_3c^2 + k_4c^3 + \frac{1}{b_1 + b_2c + b_3c^2 + b_4c^3} \quad (6)$$

Using experimental data, we can approximately identify constants in eq. (6):

$$k_1 = 65.73 \quad k_2 = -12.68 \quad k_3 = 3.47 \quad k_4 = -0.06$$

$$b_1 = 65.73 \quad b_2 = -12.68 \quad b_3 = 3.47 \quad b_4 = -0.06$$

Equation (6) becomes:

$$d = 65.73 - 12.68c + 3.47c^2 - 0.06c^3 + \frac{1}{65.73 - 12.68c + 3.47c^2 - 0.06c^3} \quad (7)$$

It is easy to find that the threshold value of concentration is $c_0 = 2$ and minimal fiber diameter is 53.8 nm, which agree well with experimental data, see fig. 2.

Discussion and conclusion

In this paper, the effect of FeCl_3 concentration on fiber diameter of electrospun PVDF membrane has been investigated. All additives will greatly affect morphology of nanofibers, this is because the additive will greatly affect the solution's density:

$$\rho = \rho_p c_p + \rho_s c_s + \rho_a c_a \quad (8)$$

where subscribes p , s and a imply PVDF, solvent, and additive, c is concentration.

Fiber diameter depends mainly upon solvent evaporation. In case $\rho_a c_a \gg \rho_s c_s$, the solvent evaporation will not affect morphology of nanofibers, so additives are widely used to control morphology of nanofibers.

With 2 wt.% addition of FeCl_3 , the average fibers diameter decreases compared with pure PDVF nanofibers. However, the average diameter of the fibers dramatically increased as the concentration of FeCl_3 increased to 10 wt.%. Meanwhile, we have also proposed a mathematical formulation of the relationship between metal inorganic salt concentration and fiber diameter based on the experimental result. This result will benefit further research with regard to diameter control in electrospinning.

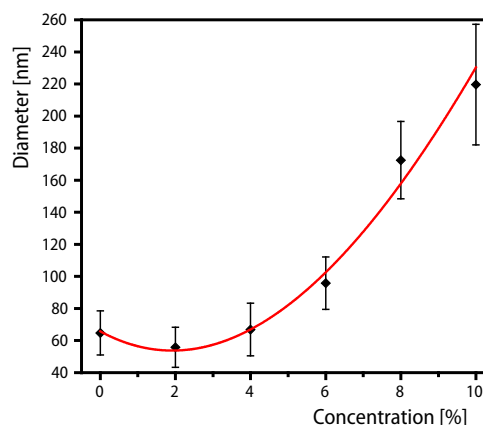


Figure 2. A plot of the fiber diameter as a function of FeCl_3 concentration

Acknowledgment

The work is supported by Priority Academic Program Development of Jiangsu Higher Education Institutions (PAPD), China Postdoctoral Science Foundation under grant No. 2015M571806 and 2016T90495, China National Textile and Apparel Council Project under grant No. 2015011, Key Scientific Research Projects of Henan Province under grant No. 16A540001 and program of China Scholarship Council.

References

- [1] Liu, Z., et al., Active Generation of Multiple Jets for Production Nanofibers with High Quality and High Throughput, *Material & Design*, 94 (2016), Mar., pp. 496-501
- [2] Liu, Z., et al., Tunable Surface Morphology of Electrospun PMMA Fiber Using Binary Solvent, *Applied Surface Science*, 364 (2016), Feb., pp. 516-521
- [3] He, C. H., et al., Bubbfil Spinning for Fabrication of PVA Nanofibers, *Thermal Science*, 19 (2015), 2, pp. 743-746
- [4] Liu, P., et al., Micro-Nanofibers with Hierarchical Structure by Bubbfil-Spinning, *Thermal Science*, 19 (2015), 4, pp. 1455-1456
- [5] Cengiz, F., et al., Influence of Solution Properties on the Roller Electrospinning of Poly(vinyl alcohol), *Polymer Engineering and Science*, 50 (2010), 5, pp. 936-943
- [6] Teeradech, J., et al., Effect of Solvents on Electro-Spinnability of Polystyrene Solutions and Morphological Appearance of Resulting Electrospun Polystyrene Fibers, *European Polymer Journal*, 41 (2005), 3, pp. 409-421
- [7] Huang, Z. M., et al., A Review on Polymer Nanofibers by Electrospinning and their Applications in Nanocomposites, *Composites Science and Technology*, 63 (2003), 15, pp. 2223-2253
- [8] Greiner, A., et al., A Electrospinning: A Fascinating Method for the Preparation of Ultrathin Fibres, *Angewandte Chemie – International Edition*, 46 (2007), 30, pp. 5670-5703
- [9] Liu, P., et al., Facile Preparation of Alpha- Fe_2O_3 Nanobulk via Bubble Electrospinning and Thermal Treatment, *Thermal Science*, 20 (2016), 3, pp. 967-972
- [10] Liu, Z., et al., Effect of Na_2CO_3 Degumming Concentration on LiBr-FORMIC ACID-Silk Fibroin Solution Properties, *Thermal Science*, 20 (2016), 3, pp. 985-991
- [11] Li, Y., et al., Bubbfil Electrospinning of PA66/Cu Nanofibers, *Thermal Science*, 20 (2016), 3, pp. 993-998
- [12] Zhang, Y., et al., Research on Morphologies of Polyvinyl Alcohol/Milk Nanofibers, *Thermal Science*, 20 (2016), 3, pp. 961-966
- [13] Zhao, L., et al., Microstructure and Property of Regenepercentaged Silk Fibroin/Chitosan Nanofibers, *Thermal Science*, 20 (2016), 3, pp. 979-983

- [14] Liu, Y., He, J. H., Bubble Electrospinning for Mass Production of Nanofibers, *International Journal of Nonlinear Sciences and Numerical Simulation*, 8 (2007), 3, pp. 393-396
- [15] Ren, Z. F., *et al.*, Effect of Bubble Size on Nanofiber Diameter in Bubble Electrospinning, *Thermal Science*, 20 (2016), 3, pp. 845-848
- [16] Shen, J., *et al.*, Primary Study of Ethyl Cellulose Nanofiber for Oxygen-Enrichment Membrane, *Thermal Science*, 20 (2016), 3, pp. 1008-1009
- [17] Li, H., *et al.*, Influence of Nano-Fiber Membranes on the Silver Ions Released from Hollow Fibers Containing Silver Particles, *Thermal Science*, 20 (2016), 3, pp. 859-862
- [18] Cui, Q. N., *et al.*, Effect of Temperature on the Morphology of Bubble-Electrospun Nanofibers, *Thermal Science*, 18 (2014), 5, pp. 1707-1709
- [19] He, J. H., *et al.*, Effect of Concentration on Electrospun Polyacrylonitrile (PAN) Nanofibers, *Fibers and Polymers*, 9 (2008), 2, pp. 140-142