

THE EFFECT OF MOISTURE CONTENT ON THE HARDGROVE GRINDABILITY INDEX OF COAL FROM THE KOLUBARA BASIN

by

Marko O. OBRADOVIĆ*, **Nikola V. KARLIČIĆ**, **Dušan M. TODOROVIĆ**,
Dejan B. RADIĆ, and **Aleksandar M. JOVOVIĆ**

Faculty of Mechanical Engineering, University of Belgrade, Belgrade, Serbia

Original scientific paper
<https://doi.org/10.2298/TSCI230529145O>

In order to obtain data on the effect of moisture content on the grindability of coals, experimental research was conducted. The experiment included six samples of coal from the Kolubara basin. The samples were selected based on experimentally obtained values of their Hardgrove grindability index (HGI), in order to cover the entire range of experimental HGI values. In addition to determining the HGI, proximate, and petrographic analyses were performed on all samples. Lignites are naturally tough, soft, and greasy when in a moist state. By reducing the moisture content, lignites become more brittle. For this reason, Hardgrove grindability index values have different values depending on the moisture content at which they are determined. The HGI has a non-linear dependence on the moisture content of the coal. All curves have two inflection points, one minimum and one maximum value of Hardgrove grindability index in the tested range. The minimum values of HGI are in the range of 15-22% of the mass fraction of total moisture in coal, while the maximum values of HGI are for a total moisture content of 5-13%. In the case of high moisture content in coal, the obtained high values of HGI may not reflect the true grindability of the coal. These values could be misleading and not necessarily indicative of the coal inherent characteristics. Instead, they could be a result of the imperfections in the Hardgrove method used to determine the grindability index of coal with high moisture content.

Key words: coal, lignite, moisture, HGI

Introduction

Grindability of coal is an important parameter used in design of coal comminution plants (*i.e.* mill plants). Coal grindability is determined by HGI and it is one of the characteristics of coal that directly affect capacity of pulverized coal mill [1, 2].

The high moisture content of lignite results in lower calorific value and larger sensitivity to spontaneous combustion, which increases fuel consumption and the cost in storage and transportation. Therefore, drying of lignite in pulverizes before combustion is necessary. Moisture in lignite affect pulverizes performance and combustion efficiency. Drying of lignite can change its grindability.

Studies [3, 4] shown that pre-drying of lignite can increase the combustion efficiency of power plant boilers burning low-rank coal by 2-4% on average. Optimizing moisture content of lignite in advance is an effective way to improve the pulverization process, to enhance thermal boiler efficiency, and hence to reduce coal consumption.

* Corresponding author, e-mail: mobradovic@mas.bg.ac.rs

Results of experimental investigations [5] shows that the grindability of coal varies in a nonlinear way with moisture. General pattern for the HGI curves is an S-shape. Similar results are reported in [6].

The influence of moisture on the grindability of coals has been particularly examined in lower-rank coals, where it poses a specific problem [7]. Studies conducted on lignite from the Dakota state [8] have revealed that at a moisture content of 10%, the HGI value was 55. However, at a moisture content of 26%, its value drops to 43, and then it rises again to 55 at a moisture content of 38%.

Vuthaluru *et al.* [9] investigated effects of moisture and coal blending on HGI for low-rank sub-bituminous Western Australia coals (Collie coalfield). Grindability test on coal samples of varied moisture content showed significant effect of moisture content on HGI values.

The effect of moisture on Shengli lignite breakage behavior and energy efficiency was studied experimentally using a standard Hardgrove mill fitted with a wattmeter [10]. Results showed that the energy-size reduction process for grinding lignite is markedly influenced by moisture occurrence and content. The energy efficiency was also significantly improved as the moisture content of lignite was reduced to below the air-dried level. The air-dried moisture content was the inflecting point for lignite grinding in the Hardgrove mill.

Saramak and Kleiv [11] showed that excess moisture could cause a decrease in grindability and produce lower throughputs of comminution circuits.

Many studies analyze the effect on coal grindability based on proximate and ultimate analysis of coal, as well as petrography [12-16].

As the moisture content of coal is one of the major factors affecting the grindability of coal, this paper investigates the effect of moisture content on HGI values of coal from the Kolubara basin.

Experimental investigations

Experimental research was conducted to obtain data on the effect of moisture content on the grindability of coals. Out of a total of 65 samples of lignite from the Kolubara basin [12], the experiment included six coal samples from the Kolubara basin. The selection of samples was based on the experimentally obtained values of their grindability (HGI values), aiming to cover the entire range of experimental HGI values from the lowest to the highest. Additionally, not only proximate analysis but also organic-geochemical and petrographic analysis [17] were performed on the aforementioned samples.

The determination of the HGI values of the coal samples was conducted in accordance with the ISO 5074 standard.

The proximate analysis of the coal samples was conducted in accordance with international standards, specifically:

- ISO 5071-1 – Brown coals and lignites – Determination of the volatile matter in the analysis sample,
- ISO 1171 – Solid mineral fuels – Determination of ash content,
- ISO 5068-1 – Brown coals and lignites – Determination of moisture content – Part 1: Indirect gravimetric method for total moisture, and
- ISO 5068-2 – Brown coals and lignites – Determination of moisture content – Part 2: Indirect gravimetric method for moisture in the analysis sample.

The analysis of coal lithotypes was performed according to the standards set by the International Committee for Coal and Organic Petrology (ICCP). The description of lithotypes was carried out based on the classification developed by Jacob [18] and modified by Ercegovic

[19]. Maceral analysis was performed on a Leitz DMPL microscope under monochromatic and ultraviolet reflected light, with a 40× objective lens and a 10× eyepiece, on 500 points (ISO 7404-3) in oil immersion. The maceral description followed the terminology developed by the ICCP for huminite, liptinite, and inertinite nomenclature. The determination of total organic carbon content was performed after the removal of carbonates with diluted hydrochloric acid (in a ratio of 1:3 v/v) using a Vario EL III CHNS/O analyzer. The isolation of soluble organic matter (maltenes) into saturated hydrocarbons, aromatic hydrocarbons, and NSO fractions was carried out on a Kohnen-Willsch medium pressure liquid chromatography (MPLC) chromatograph following a standard procedure. The saturated and aromatic hydrocarbon fractions were analyzed using gas chromatography-mass spectrometry (GC-MS) technique and single ion monitoring (SIM) method [17].

At the beginning of the testing, the determination of total moisture content and the mass of the absolutely dry sample was performed to monitor the change in total mass over days. The sample mass measurements were carried out daily, and the mass fraction of total moisture in the sample was calculated.

The initial determination of HGI values was conducted when the sample reached a total moisture content of approximately 30%, and then at every 5% decrease in moisture content, namely 25%, 20%, 15%, 10%, and 5%. The samples were air-dried, taking into account atmospheric conditions, which resulted in some samples requiring a longer time to reach the desired mass fractions of moisture. Upon reaching the desired moisture content, an appropriate mass of coal was taken from the total sample using a splitter to obtain a representative sample for determining the HGI value of the considered sample.

To demonstrate the trend of decreasing grindability for sample no. 5 after the maximum, the sample was dried in a dryer at 40 °C to reduce the moisture mass fraction below 5.25%. The drying was performed in a dryer because, due to atmospheric conditions and low moisture content, it was not possible to further extract moisture from the sample through natural means. After drying at 40 °C, the determination of total moisture content in the sample was carried out following the ISO 5068-1 standard.

Results and discussion

In tab. 1, the results of the proximate analysis of the selected coal samples are presented.

What should be noted is the different impact of air-dry moisture and residual moisture content on grindability. Residual moisture has a clear negative effect on grindability, while the effect of air-dry moisture causes varying impacts [12]. Air-dry moisture leads to the sticking and agglomeration of coal mass.

In tab. 2, the results of lithotype composition of the coal samples are presented, while tab. 3 shows the results of maceral composition.

Prevailing lithotype in all studied samples is matrix coal, except sample 1 for which the xylite-rich coal is the dominant type, tab. 2. Brown xylite type is the dominant xylite-rich type in almost all samples. Only in the sample 1 dark yellow type prevails.

Huminite is the prevailing maceral group in all samples, tab. 3. Most abundant macerals are textinite, ulminite and densinite with a variable amount of attrinite and corpohuminite. Content of gelinite is low. Liptinite ranges from 4.2-8.3 vol.%. Percentages of inertinite range from 3.0-4.2 vol.%. The content of mineral matter varies between 6.3 vol.% and 30.6 vol.%.

Table 1. Proximate analysis of coal samples

No.	HGI [–]	V _a [%]	W _{h,a} [%]	A _a [%]	WG [%]	W _h [%]	W [%]	V [%]	A [%]
1	30.7	39.54	12.51	19.20	41.93	7.27	49.20	22.96	11.15
2	35.8	39.30	12.10	20.42	44.78	6.68	51.46	21.70	11.28
3	42.0	38.62	11.24	22.96	43.48	6.35	49.83	21.83	12.98
4	44.9	37.11	8.79	33.26	45.20	4.82	50.02	20.34	18.23
5	48.5	33.61	9.14	36.48	42.54	5.25	47.79	19.31	20.96
6	56.9	31.93	7.99	42.49	41.37	4.68	46.05	18.72	24.91

Table 2. Lithotype composition [wt.%] of studied samples

No.	Matrix coal	Xylite-rich coal							Dopplerite coal	Charcoal	Mineral rich coal	Mineral matter
		Pale yellow type	Dark yellow type	Brown type	Black type	Yellow ^a	Brown and black ^b	Total				
1	17.20	0.00	45.75	33.70	0.93	45.75	34.63	80.38	0.16	0.08	1.40	0.78
2	45.55	0.02	20.78	29.47	2.22	20.80	31.69	52.49	0.05	0.02	0.60	1.29
3	57.85	0.00	11.68	28.55	1.00	11.68	29.55	41.23	0.04	0.02	0.59	0.27
4	56.20	0.00	16.26	24.47	0.98	16.26	25.45	41.71	0.65	0.03	0.85	0.56
5	58.47	0.03	15.89	14.72	1.15	15.92	15.87	31.79	0.06	0.03	3.54	6.11
6	47.23	0.001	6.48	31.68	0.03	6.48	31.71	38.19	0.03	0.07	8.32	6.19

Note: (a) Xylite yellow = pale yellow type + dark yellow type and (b) Xylite brown and black = brown type + black type

Organic geochemical properties and molecular composition of the organic matter in detail are given in [12, 17].

The dependency of moisture changes in the samples over time is presented in fig. 1.

The experimentally obtained results of HGI values for different mass fractions of total moisture in coal samples are presented in tab. 4 and figs. 2-7.

As seen in figs. 2-7, the HGI exhibits a non-linear dependence on the mass fraction of total moisture in coal. All curves have two inflection points, one minimum and one maximum HGI value within the tested range. The minimum HGI values correspond to a mass fraction of total moisture in the range of 15-22%, while the maximum HGI values are observed at moisture fractions of 5-13%.

The obtained high HGI values for samples with high moisture content should be interpreted with caution. Based on the obtained curves, figs. 2-7, one might mistakenly conclude that it is easier to grind coal with high moisture content compared to coal with a residual moisture content. However, this contradicts practical experience, which dictates that quality coal grinding cannot be achieved without drying it in mills. Additionally, it can be inferred that the Hardgrove method for determining HGI values in high moisture content coal is not applicable and does not provide realistic practical results.

One possible explanation for the obtained high HGI values at high moisture fractions in coal lies in the following. During the determination of HGI values for samples with high moisture content, coal adhesion was observed both on the balls and on the working bowl of the

Table 3. Maceral composition [vol.%] of studied samples

Maceral	Sample					
	1	2	3	4	5	6
Te	53.6	44.7	45.4	29.1	37.6	13.3
Ul	5.6	14.0	11.7	11.9	15.3	9.0
At	1.8	5.9	0.9	8.0	4.7	10.1
De	12.5	13.8	20.9	25.5	16.6	21.4
Ge	0.6	0.2	1.7	0.6	0.5	0.9
Ch	4.5	3.2	5.1	3.9	3.7	2.5
HUM	78.6	81.8	85.7	79.0	78.4	57.2
Sp	2.1	0.7	0.9	1.1	1.2	3.0
Cu	0.3	0.5	0.0	0.3	0.3	0.2
Re	1.2	1.0	0.3	2.2	1.1	1.1
Su	3.2	1.0	2.2	1.1	1.1	2.3
Ld	1.5	1.0	0.9	0.6	1.3	1.4
LIP	8.3	4.2	4.3	5.3	5.0	8.0
Fu	0.3	1.5	0.0	0.3	0.3	0.0
Sf	0.0	0.0	0.6	0.8	0.3	0.5
Ma	0.3	0.0	0.0	0.3	0.0	0.5
Fn	2.7	0.5	0.9	0.8	1.2	1.4
Id	0.6	1.4	2.2	0.8	1.3	1.8
INER	3.9	3.4	3.7	3.0	3.1	4.2
MM	9.2	10.6	6.3	12.7	14.5	30.6

Note: Te – textinite, Ul – ulminite, At – attrinite, De – densinite, Ge – gelinite, Ch – corpohuminite, HUM – total huminite, Sp – sporinite, Cu – cutinite, Re – resinite, Su – suberinite, Ld – liptodetrinite, LIP – total liptinite, Fu – fusinite, Sf – semifusinite, Ma – macrinite, Fn – funginite, Id – inertodetrinite, INER – total inertinite, MM – total mineral

Figure 1. The dependence of the change in the mass fraction of total moisture in the samples

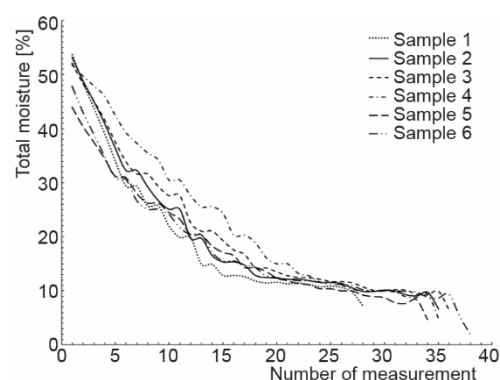
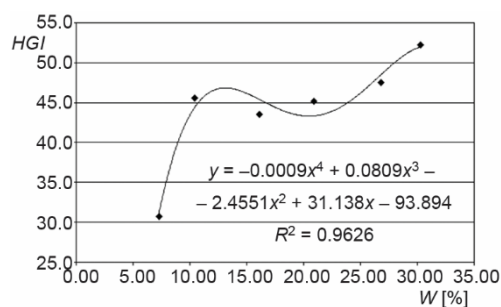
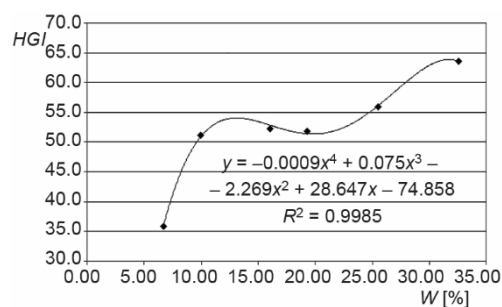
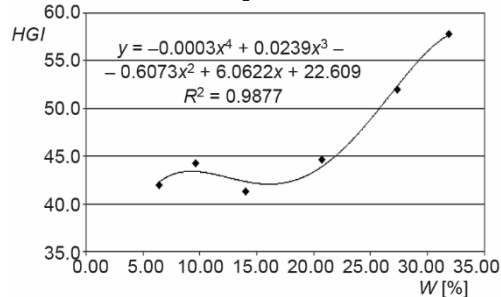
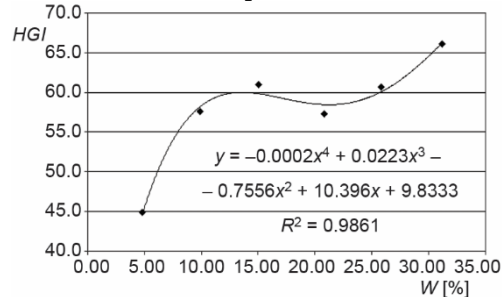
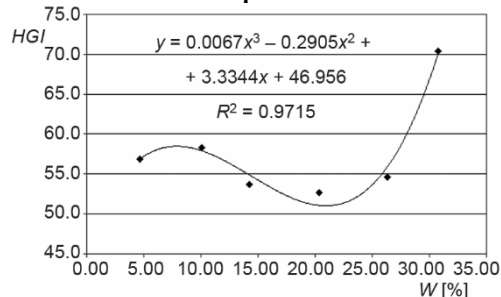
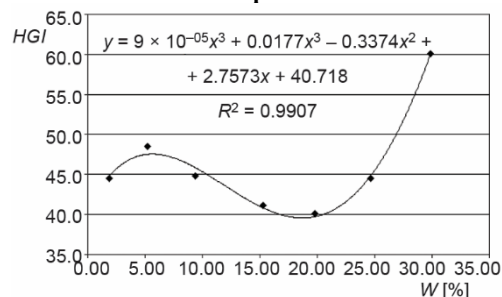


Table 4. Experimentally obtained results of HGI values for different mass fractions of total moisture

Sample 1		Sample 2		Sample 3		Sample 4		Sample 5		Sample 6	
W. [%]	HGI	W. [%]	HGI	W. [%]	HGI	W. [%]	HGI	W. [%]	HGI	W. [%]	HGI
30.27	52.3	32.60	63.6	31.88	57.8	31.17	66.1	30.76	70.4	29.88	60.1
26.79	47.5	25.51	56.0	27.37	52.0	25.81	60.7	26.33	54.6	24.71	44.5
20.92	45.2	19.29	51.9	20.72	44.6	20.79	57.3	20.39	52.7	19.81	40.1
16.07	43.5	16.06	52.3	14.01	41.3	15.05	61.0	14.24	53.7	15.32	41.1
10.42	45.6	9.93	51.1	9.61	44.3	9.91	57.6	10.12	58.3	9.42	44.8
7.26	30.7	6.68	35.8	6.41	42.0	4.82	44.9	4.68	56.9	5.25	48.5
										1.90	44.5

**Figure 2. Effect of total moisture content on HGI values for sample 1****Figure 3. Effect of total moisture content on HGI values for sample 2****Figure 4. Effect of total moisture content on HGI values for sample 3****Figure 5. Effect of total moisture content on HGI values for sample 4****Figure 6. Effect of total moisture content on HGI values for sample 5****Figure 7. Effect of total moisture content on HGI values for sample 6**

apparatus. This coal adhesion hampers the coal flow that has not entered the grinding process in the Hardgrove mill. In other words, an undetermined amount of coal is repeatedly ground (as not the entire sample enters the grinding process), resulting in a fraction that passes through the 75 [μm] sieve, leading to unrealistically high HGI values. Therefore, the high HGI values in samples with high moisture content are a consequence of method imperfections (mill design) rather than coal characteristics.

The increase in HGI values after the minimum is explained by the weakening of the coal structure due to a decrease in moisture content, leading to the appearance of cracks in the coal structure during drying. The subsequent decrease in HGI values as the moisture content approaches zero is explained by the characteristics of dry coal ash. Similar results regarding the influence of moisture on HGI values have been reported in [5, 6].

Through experimental investigations of the M-12 beater wheel mill in thermal power plant Nikola Tesla B, it was determined that the average moisture content in the pulverized coal was 13.15%. Therefore, it can be considered that the mill operates with approximately optimal moisture content in terms of HGI values. It should be noted that the guaranteed moisture content value in the pulverized coal for the M-12 mill was 10% [2, 12].

Conclusions

The study provides an analysis of the influence of total moisture content in coal on certain values. The experiment included six samples of coal from the Kolubara basin. In addition, petrographic and organic geochemical analyses were previously conducted on all six studied samples.

The moisture content in coal has a significant influence on the HGI. It is important to note that the relationship between moisture content and HGI is not linear. Experimentally obtained curves have two inflection points, one minimum and one maximum HGI value within the tested range.

In the case of high moisture content in coal, the obtained high values of HGI should be taken with caution to avoid drawing the incorrect conclusion that coal with high moisture content is easier to grind. This statement is in line with practical experience, which suggests that effective coal grinding can not be achieved without drying it beforehand.

On the other hand, lower moisture content generally leads to higher HGI values. When coal has a lower moisture content, it becomes drier and more brittle. This increased brittleness facilitates the grinding process, as the coal particles are more easily broken and pulverized.

The effect of moisture on grindability varies depending on other factors such as coal rank, mineral matter content, and particle size distribution. Therefore, for the future work, it is necessary to consider these factors along with moisture content when assessing the grindability of coal using the HGI test.

Overall, controlling the moisture content of coal is essential in optimizing its grindability and subsequent utilization in various industrial processes, such as coal pulverization for power generation in thermal power plants or coal preparation for industrial applications.

Acknowledgment

The presented results of the UB-FME here have been financed and supported by Ministry of Science, Technological Development and Innovation of the Republic of Serbia, contract No. 451-03-65/2024-03/200105 dated 5.2.2024.

Nomenclature

A – ash content in coal (mass fraction), [%]	W – total moisture in coal (mass fraction), [%]
A_a – ash content in analysis sample of coal (mass fraction), [%]	WG – air-dry moisture (mass fraction), [%]
V – volatile matter in coal (mass fraction), [%]	W_h – residual moisture content, [%]
V_a – volatile matter in analysis sample of coal (mass fraction), [%]	$W_{h,a}$ – moisture content in analysis sample of coal (mass fraction), [%]

References

- [1] Radić, D. B., *et al.*, A Study on the Grindability of Serbian Coals, *Thermal Science*, 15 (2011), 1, pp. 267-274
- [2] Obradović, M. O., *et al.*, Practical Assessment of Grinding Capacity and Power Consumption Based on Hardgrove Grindability Index and Coal Characteristics, *Thermal Science*, 23 (2019), Suppl. 5, pp. S1533-S1542
- [3] Weigl, K., *et al.*, Increasing Power Plant Efficiency by Fuel Drying, *Computers and Chemical Engineering*, 23 (1999), Suppl. 1, pp. 1-4
- [4] Kakaras, E., *et al.*, Computer Simulation Studies for the Integration of an External Dryer Into a Greek Lignite-Fired Power Plant, *Fuel*, 81 (2002), 5, pp. 583-593
- [5] Jensen, E. J., Fryer, J. F., An Investigation of the Grindability of Alberta Subbituminous Coals, Mimeographed Circular No. 26, Research Council of Alberta, Edmonton, Alb., USA, 1958
- [6] Novaković, L., *Grindability Of Coal Matter* (in Serbian), Mining Institute, Belgrade, 1976
- [7] Azahari, H. L., The Effect of Moisture on the Grindability of Indonesian Coals, Master of Metallurgy (Hons.) Ph. D. thesis, Department of Materials Engineering, University of Wollongong, Wallongon, Australia, 1990, <https://ro.uow.edu.au/theses/2590>
- [8] Lowry H. H., *Chemistry Of Coal Utilization, Supplementary Volume*, John Wiley & Sons, New York, USA, 1962
- [9] Vuthaluru, H. B., *et al.*, Effects of Moisture and Coal Blending on Hardgrove Grindability Index of Western Australian Coal, *Fuel Processing Technology*, 81 (2003), 1, pp. 67-76
- [10] Yang, Y., *et al.*, Effect of Moisture on Energy-Size Reduction of Lignite Coal in Hardgrove Mill, *Fuel*, 270 (2020), 117477
- [11] Saramak, D., Kleiv, R. A., The Effect of Feed Moisture on the Comminution Efficiency of HPGR Circuits, *Minerals Engineering*, 43-44 (2013), Apr., pp. 105-111
- [12] Obradović, M., Research and Comparison of the Influence of Low Rank Coals Characteristics on their Grindability and Milling Process Parameters (in Serbian), Ph. D. thesis, University of Belgrade Faculty of Mechanical Engineering, Belgrade, 2015
- [13] Chelgani, S. C., *et al.*, Prediction of Coal Grindability Based on Petrography, Proximate And Ultimate Analysis Using Multiple Regression and Artificial Neural Network Models, *Fuel Processing Technology*, 89 (2008), 1, pp. 13-20
- [14] Hower, J. C., Interrelationship of Coal Grinding & Petrology, *Minerals&Metallurgical Processing*, 15 (1998), 3, pp. 1-16
- [15] Hower, J. C., *et al.*, Soft Modelling of the Hardgrove Grindability Index of Bituminous Coals: An Overview, *International Journal of Coal Geology*, 247 (2021), 103846
- [16] Sengupta, A. N., An Assessment of Grindability Index of Coal, *Fuel Processing Technology*, 76 (2002), 1, pp. 1-10
- [17] Životić, D., *et al.*, Petrological and Organic Geochemical Properties of Lignite from the Kolubara and Kostolac Basins, Serbia: Implication on Grindability Index, *International Journal of Coal Geology*, 131 (2014), Sept., pp. 344-362
- [18] Jacob, H., Die Petrographische Bestimmung Das Xylitgehaltes Von Weichbraunkohlen, *Geologisches Jahrbuch, Band 79* (1961), pp. 145-172
- [19] Ercegovac, M., Micropetrographic Composition of Coal from Stanari with Special Emphasis on the Content of Xylite and Features of Briquetting, *Buletin of Mines*, 28 (1989), pp. 28-37